


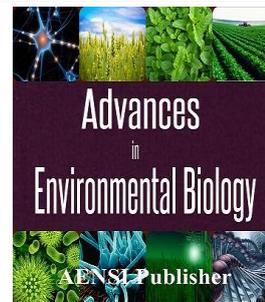

AENSI Journals

Advances in Environmental Biology

ISSN-1995-0756 EISSN-1998-1066

Journal home page: <http://www.aensiweb.com/AEB/>

Mechanical properties of cement mortar containing nanoparticles

Mohammad Reza Arefi

Department of Civil Engineering, Payam Noor University, Tehran, Iran.

ARTICLE INFO

Article history:

Received 11 October 2014

Received in revised form 21 November 2014

Accepted 25 December 2014

Available online 16 January 2015

Keywords:

Mechanical properties, nanoparticles, cement mortar, SEM, microstructure.

ABSTRACT

In this article, the effects of two nano-sized powders (nano-SiO₂ and nano-Fe₂O₃) on the compressive strength, tensile strength and flexural strength of cement mortar were investigated. The results show that the mechanical properties of samples containing 1 and 3 percent nanoparticles are desirable than the ordinary cement mortar. But by increasing nanoparticles up to 5 percent, the mechanical properties reduce severely. However, SEM study about the microstructure of cement mortar containing nanoparticles and ordinary cement mortar showed that nanoparticles reduces the CaOH₂ crystals and fills the pores and increases the density of cement mortar.

© 2015 AENSI Publisher All rights reserved.

To Cite This Article: Mohammad Reza Arefi., Mechanical properties of cement mortar containing nanoparticles. *Adv. Environ. Biol.*, 9(2), 282-286, 2014

INTRODUCTION

By using extensively mineral addition for the improve performance of cement-based materials. Partial replacement of cement with mineral additions improves the performance cement-based materials in fresh and hardened states. In the recent years, using nanoparticles has developed due to its small size possess unique properties such as high specific surface area and high activity. Several reports are present about adding nanoparticles to cement materials, that most of them have focus on the silica nanoparticles. Ye Qing et al, have shown that adding SiO₂ nanoparticles to hardened cement paste increases the compressive strength and bond strength of paste-aggregate interface more than silica fume addition which means because of SiO₂ nanoparticles due to high specific surface and amount of atoms in the surface has higher chemical reaction area [17].

Wang Baomin and et al showed that adding SiO₂ nanoparticles can improve the microstructure of the cement and result in the increase of freezing resistance with high performance concrete [9]. Mohammad Reza Arefi and et al, have studied the effect of adding SiO₂ particles with different diameters and different amount to the cement mortar. The research results showed that nanoparticles due to higher specific surface area improve the resistance properties and water permeability of cement mortar than the micro-particles. Then, samples consisting nanoparticles, samples with nano-silica large diameters have better effect in improving the mechanical properties. And because of the possibility of increase agglomeration of nanoparticles is more with smaller diameter [3].

Study has been conducted with focus on comparison effect of adding different nanoparticles. For example, study which has compared the addition of TiO₂ nanoparticles with SiO₂, the result shows that the abrasion resistance and flexural fatigue performance of concrete containing TiO₂ nanoparticles is more than the abrasion resistance of concrete containing the same amount of SiO₂ nanoparticles [11,12]. Also, improving of resistance to chloride penetration for the concrete containing TiO₂ is more than the concrete containing the same amount of SiO₂ [18]. There exists report about the addition of Fe₂O₃ nanoparticles to cement-based materials. Ali Nazeri and et al have researched the effect of addition Fe₂O₃ nanoparticles with mechanical properties and percentage of water absorption of concrete which is cured in water and saturated limewater. Their research results showed that by addition of nanoparticles till two percent improves the mechanical properties and concrete penetration that the amount of this improvement for the sample is more which have cured in limewater [13,14]. The aim of this study is to research the effect of adding nanoparticles to cement mortar and to find optimized percentage of adding nanoparticles and also finding mechanism to improve the mechanical properties of cement mortar.

MATERIAL AND METHODS

Materials and mixture proportions:

ASTM C 150 [4] Type II portland cement was used. The Fe₂O₃ nanoparticles with average particles size of 20 nm and SiO₂ nanoparticles with average particles size of 30 nm which were purchased from Skyspring Nanomaterials Inc were used. The characteristics of the nanoparticles were shown in Table 1. The superplasticizer (a commercial sulphonated melamine formaldehyde polymer) with relative density of 1.15 was employed to achieve good workability. The content was adjusted for each mixture to ensure that no segregation would occur. Also, the distilled water was used for preparing all mixtures. The fine aggregate was crushed silica sand with a fineness modulus of 2.4, the apparent density of 3.33 gr/cm³. The sand was graded according to ASTM C33 [5] standard. The largest diameter of these aggregate particles was 4.75 mm.

Table 1: Characteristics of nanoparticles

Item	Average particle size	Specific surface area(m ² /g)	Purity (%)	Purity(%)
SiO ₂	20nm	200	99.5	99.9%
Fe ₂ O ₃	30nm	60	99.7	

The proportions of the mixtures were presented in table 2. The ratio of the water to binder (the cement and nanoparticles) was chosen 0.42. In this study the mixtures were prepared with the cement replacement of 1%, 3% and 5% by weight of binder.

Table 2: Mix proportion of samples

Mixture type	Water	Cement	Sand	Nano-Fe ₂ O ₃	*SP
*CO	150	360	1800	-	-
1NS	150	356.4	1800	3.6	3.68
3NS	150	349.2	1800	10.8	4.29
5NS	150	342	1800	18	4.9
1NF	150	356.4	1800	3.6	3.68
3NF	150	349.2	1800	10.8	4.29
5NF	150	342	1800	18	4.9

*SP: superplasticizer

Sample preparation:

The high homogenous dispersion of nanoparticles strongly depends on stable suspension preparation. Hence nano powder was mixed with the distilled water and stirred for 6-10 hours by rotational speed of 250-300 rpm. At first, the suspension of the nanoparticles and the superplasticizer were mixed in the mixer for 30 second, where the cement was added to this mixture simultaneously. Thereafter, the sand, from finest to coarsest, was added gradually to the mixture, and the mixing continued until the complete homogenization of the mixture. Then, the mortar was poured into the standard mold. For tensile test, the briquette specimens with 75×25×25 mm dimension were utilized. The mortar was poured in two layers, both of them compressed by 4 impacts of a steel rod. In order to prepare the specimens of the compressive tests, the mortar was poured into molds to form cubes of size 50×50×50 mm in three layers alternatively, which all layers compressed by 10 impacts of a steel rod. For the flexural test, the mortar was poured into the molds with dimensions of 40×40×160 mm in two layers. Each layer was compacted by 15 impacts of a steel rod. The molded specimens were covered with a plastic layer for 24 hours and then were cured in water at the room temperature up to end of the seventh day. Six specimens were prepared for each test and the average result was reported.

Test methods:

The apparatus made by ELE Company, England was used for performing the mechanical tests. The microstructure of the specimens was studied by the scanning electron microscopy (SEM) Hitachi S-4160. Compressive tests were carried out according to the ASTM C109 [6] and tensile tests were carried out according to the ASTM C190 [7]. Flexural tests were carried out according to ASTM C348 [8].

RESULTS AND DISCUSSION

Mechanical properties:

Results of compressive strength, tensile strength after curing for seven days is shown in table 3 and figure 1. It can be understood from the table that by adding nanoparticles till 3 percent compressive, tensile and flexural strength increases and then by increasing the quantity of nanoparticles to 5 percent, strength reduces less than the ordinary cement mortar. This may be due to the fact that the quantity of nanoparticles present in the mix is higher than the amount required to combine with the liberated lime during the process of hydration, thus leading

to excess silica leaching out and causing a deficiency in strength as it replaces part of the cement material and does not contribute to its strength [1].

This issue is because nanoparticles due to their high surface energy have the tendency towards agglomeration. When nanoparticles are over added to the mortar it is not uniformly distributed in cement mortar and due to agglomeration weak areas appear in the cement mortar. Whereas, few amounts of nanoparticles even if not distributed uniformly increase the strength, this is because that small quantity of nanoparticles agglomeration does not create weak zone [10].

Table 3: Mechanical properties of samples

0	Compressive strength at the 7 th day			Tensile strength at the 7 th day			Flexural strength at the 7 th day		
	Target (MPa)	Enhanced (%)	extent	Target (MPa)	Enhanced (%)	extent	Target (MPa)	Enhanced (%)	extent
CO	11.96	-		1.51	-		2.2	-	
1NS	24.866	107.85		1.501	0		2.39	8.6	
3NS	28.533	138.5		2.257	50		3.87	75.9	
5NS	23.767	98.66		1.273	-15.33		2.2	0	
1NF	18.71	56.44		2.03	34.43		3.3	50	
3NF	20.81	74		2.25	49		4.3	95.45	
5NF	10.08	-9.7		1.25	-17.22		1.8	-18.18	

The mechanisms of nanoparticles that causes the increases of strength of cement mortar it can be defined as the nanoparticles because of high specific surface area causes the consumption of crystalline $\text{Ca}(\text{OH})_2$ which quickly formed during the hydration of cement process and fills the void structure of C-S-H gel and finally the hydrated products are made denser and compact.

In other words, when nanoparticles are uniformly distributed in the cement mortar, each particle is contained in a cube pattern and the distance between nanoparticles can be adjusted. After the beginning of cement hydration process, nanoparticles due to their high activity develops and accelerate the cement hydration and hydrate products of nanoparticles are surrounded as kernel. If the quantity and distance between these nanoparticles is suitable, nanoparticles prevents the growth of $\text{Ca}(\text{OH})_2$ crystals [12]. The past research of these researchers show that with excessive increase of nanoparticles quantity, the nanoparticles distance decreases and $\text{Ca}(\text{OH})_2$ crystals due to limited space cannot grow enough and finally the crystal quantity is reduced [3]. This factor along with the agglomerated nanoparticles causes the mechanical properties of the sample 5NF is lower than the ordinary mortar sample.

The results show that the addition of nanoparticles, increasing amount of tensile and flexural strength is more than compressive strength, which agrees with the research results by Ali Nazeri and et al [13,14].

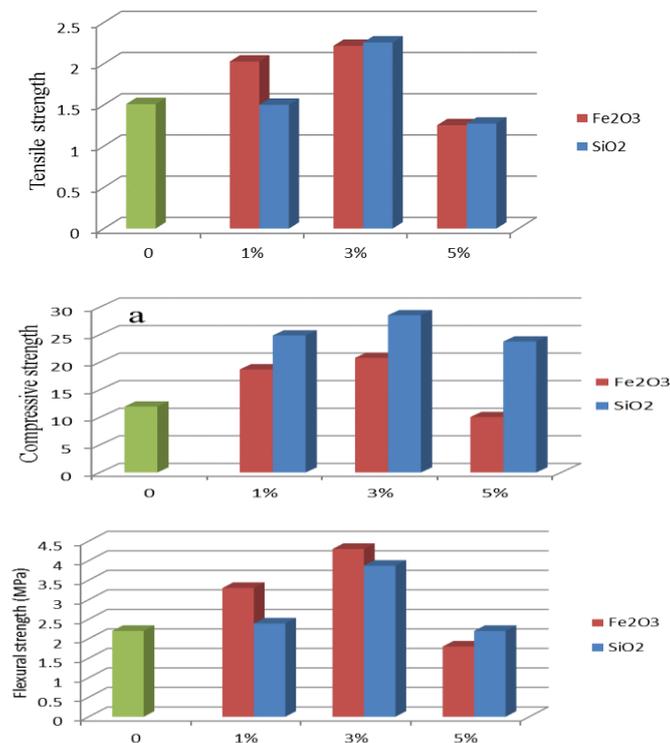


Fig. 1: (a) Compressive strength, (b) Tensile strength, and (c) Flexural strength of samples

Microstructure of samples:

To study the mechanism which improves the strength, SEM test has been conducted. The microstructure of samples is shown in figure 2. As shown in the figure, adding nanoparticles causes difference in the microstructure samples. In microstructure samples of ordinary cement mortar there exists large crystals of Ca(OH)_2 . Microstructure of cement mortar is not dense and voids can be seen. As shown in figure 2b, in sample containing 1 percent nanoparticles relative to sample of ordinary cement mortar the structure of cement mortar has become denser and the voids decreased but still large crystals of Ca(OH)_2 are observed. But, with increasing quantity of nanoparticles to 3 percent, large crystals of Ca(OH)_2 are eliminated and microstructure of cement mortar is completely denser.

As shown in figure 2d, in samples containing 5 percent nanoparticles because of the agglomeration of nanoparticles voids are formed. These microstructures with the reduction of mechanical properties in these samples are appropriate.

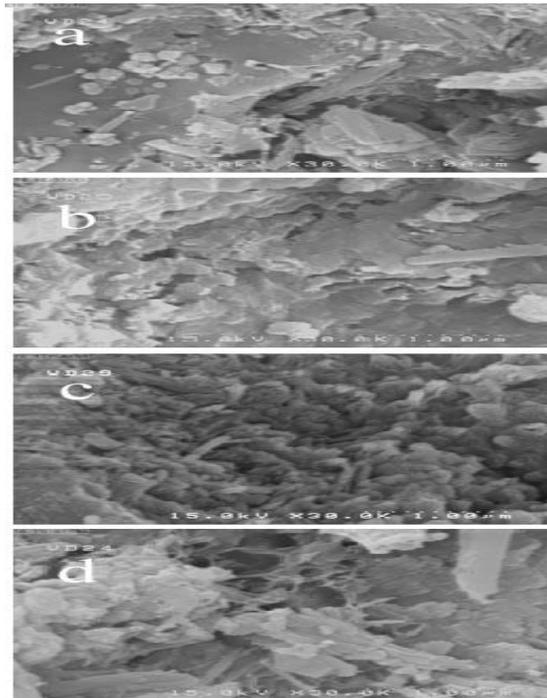


Fig. 2: Microstructure of the samples

- a) Sample of CO
- b) Sample of 1NS.
- c) Sample of 3NS
- d) Sample of 5NS

Conclusion:

With respect to the experimental results of compressive, tensile and flexural strength it is expected that adding of Fe_2O_3 nanoparticles to 3 percent weight of cement can act as a filler for strengthening the microstructure of cement and also reduces the quantity and size of Ca(OH)_2 crystals and finally structure of hydrated product is compacted and denser. But with the increase of quantity of nanoparticles to 5 percent there is decrease in nanoparticles distance and Ca(OH)_2 crystal due to limited space cannot grow to appropriate size. This factor along with the agglomerated nanoparticles causes the mechanical properties of the sample 5NF is lower than the ordinary mortar sample.

REFERENCES

- [1] Al-Khalaf, M.N., H.A. Yousift, 1984. Use of rice husk ash in concrete, *Int J Cem Compos Light weight Concr*; 6(4): 241-248.
- [2] Arefi, M.R., E. Mollaahmadi, B. AbdollahiNejand, M. Fattah, 2010. High performance self -cleaning cement mortar composite and coats prepared by TiO_2 nanoparticles, Submitted in *Journal of Materials Science*.

- [3] Arefi, M.R., M.R. Javaheri, E. Mollaahmadi, H. Zare, B. AbdollahiNejand, M. Eskandari, 2011. Silica nanoparticle size effect on mechanical properties and microstructure of cement mortar, *Journal of American Science*, 7: 231-238.
- [4] ASTM C150, 2005. Standard Specification for portland cement, American Society for Testing and Materials.
- [5] ASTM C33, 2007. Standard specification for concrete aggregates, American society for testing and materials.
- [6] ASTM C109 / C109M, 2008. Standard Test Method for Compressive Strength of Hydraulic Cement Mortars (Using 2-in. or [50-mm] Cube Specimens), American society for testing and materials.
- [7] ASTM C190, 1985. Method of test for tensile strength of hydraulic cement mortars, American Society for Testing and Materials.
- [8] ASTM C348, 2008. Standard test method for flexural strength of hydraulic-cement mortars, American society for testing and materials.
- [9] Baomin, W., W. Lijiu, F.C. Lai, 2008. Freezing Resistance of HPC with Nano-SiO₂. *J Wuhan Univ Technol-Mater(Sci. Ed)*; 23: 85-88.
- [10] Li, H., H.G. Xiao, J. Yuan, J. Ou, 2004. Microstructure of cement mortar with nano-particles. *Compos: Part B: Eng*, 35: 185-189.
- [11] Li, H., M.H. Zhang, J.P. Ou, 2007. Flexural fatigue performance of concrete containing nano-particles for pavement. *Int J Fatigue*, 29: 1292-1301.
- [12] Li, H., M.H. Zhang, J.P. Ou, 2006. Abrasion resistance of concrete containing nano-particles for pavement. *Wear*, 260: 1262-1266.
- [13] Nazari, A., S. Riahi, S. Riahi, S.F. Shamekhi and Khademno, 2010a. Influence of Fe₂O₃ nanoparticles on the compressive strength and workability of blended concrete, 6: 6-9.
- [14] Nazari, A., S. Riahi, S. Riahi, S.F. Shamekhi and Khademno, 2010b. Mechanical properties of cement mortar with Fe₂O₃ nanoparticles, 6: 94-97.
- [15] Nazari, A., S. Riahi, 2011. Fe₂O₃ nanoparticles in concrete and different curing media. *Energy and Buildings*, 43: 1480-1488.
- [16] Nazari, A., S. Riahi, 2011. Improvement compressive strength of concrete in different curing media by Fe₂O₃ nanoparticles. *Materials Science and Engineering A* 528: 1183-1191.
- [17] Ye Qing, Zhang Zenan, Kong Deyu, Chen Rongshen, 2007. Influence of nano-SiO₂ addition on properties of hardened cement paste as compared with silica fume, *Construction and Building Materials*, 21: 539-545.
- [18] Zhang, M.H., H. Li, 2011. Pore structure and chloride permeability of concrete containing nano-particles for pavement, *Construction and Building Materials*, 25: 608-616.